

Intifadhah et al

by Sahara Hamas Intifadhah

Submission date: 11-Nov-2024 10:22PM (UTC+0700)

Submission ID: 2515937407

File name: 34325-Article_Text-89472-105109-2-20240518_2.docx (282.35K)

Word count: 4777

Character count: 28887



MINI-REVIEW: THE INFLUENCE OF COATING AND DOPING ON THE CRYSTAL VOLUME AND DISCHARGE CAPACITY OF LITHIUM IRON PHOSPHATE-BASED MATERIALS AS BATTERY CATHODE

Sahara Hamas Intifadhah^{*1}, Husna Syaima²

8

¹Department of Physics, Faculty of Mathematics and Natural Sciences,
Mulawaman University, Samarinda 75123, Indonesia

²Department of Chemistry, Faculty of Mathematics and Natural Science,
Mulawaman University, Samarinda 75123, Indonesia

e-mail^{*1}: saharahamas@fmipa.unmul.ac.id

Received 18 May 2024

Published 15 October 2024

<https://doi.org/10.33369/jkf.7.2.74-83>

ABSTRAK

Baterai ion litium adalah jenis baterai isi ulang yang memiliki kapasitas tinggi, potensi elektrokimia yang baik, dan daya tahan yang kuat. Perkembangan LiFePO_4 sebagai material katoda baterai ion litium semakin meningkat dengan adanya beberapa teknik tambahan dalam proses sintesis untuk meningkatkan performa seperti teknik pelapisan dan penyisipan atom. Hal tersebut mempengaruhi volume kristal, serta sifat elektrokimia material berbasis LiFePO_4 . Metode pelapisan yang menunjukkan peningkatan nilai kapasitansi material berbasis LiFePO_4 . Sedangkan pada metode penyisipan atom, beberapa penelitian menggunakan atom Ce, Ru, Co, Na, Si, Mn, Zn dan In untuk disisipkan di atom Fe, Li, atau P pada material berbasis LiFePO_4 . Hasil yang diperoleh dari beberapa penelitian tentang sintesis material katoda LiFePO_4 menunjukkan adanya peningkatan kapasitas discharging dan peningkatan volume kristal olivine, sehingga teknik pelapisan dan penyisipan ini dapat digunakan untuk peningkatan performa elektrokimia.

Kata kunci: LiFePO_4 , Pelapisan, Penyisipan, Volume Kristal, Kapasitansi

ABSTRACT

Lithium-ion batteries are a type of rechargeable battery that has high capacity, good electrochemical potential, and strong durability. The development of LiFePO_4 as a cathode material for lithium-ion batteries has been increasing with the addition of several techniques in the synthesis process to enhance performance, such as coating and atom insertion techniques. These techniques affect the crystal volume and the electrochemical properties of LiFePO_4 -based materials. Coating methods have shown improvements in the capacitance values of LiFePO_4 -based materials. Meanwhile, in atom insertion methods, some studies have used Ce, Ru, Co, Na, Si, Mn, Zn, and In atoms to be inserted into Fe, Li, or P atoms in LiFePO_4 -based materials. Results from several studies on the synthesis of LiFePO_4 cathode materials have shown an increase in discharge capacity and an increase in the volume of olivine crystals, indicating that coating and insertion techniques can be used to improve electrochemical performance.


Keywords: LiFePO_4 , Doping, Coating, Crystal Volume, Capacity

I. INTRODUCTION

Lithium-ion battery is an electronic device that is being developed a lot because of its wide use. The lithium-ion battery is a type of secondary battery or rechargeable battery that has a high capacitance, high electrochemical potential, and good durability (1). Based on several studies, LiFePO_4 material is one lithium-ion battery cathode that has been widely developed because of its advantages compared to other cathode materials. LiFePO_4 has several advantages including high

capacitance, thermal stability, long life cycle, safety because it can be synthesized using environmentally friendly materials, and low production costs (2). One of the lithium-ion battery cathodes that have been synthesized in previous studies is from LiFePO_4 -based material (3, 4). The electrode (anode and cathode), separator, and electrolyte are the main components of a lithium-ion battery (5). The electrodes are used to release and accept the electrons. The separator functions as a barrier between the anode and cathode that ions can pass through, while the electrolyte is a liquid that functions for reduction-oxidation processes and as a medium for ion transport or transfer. The process that occurs when discharging or discharging, namely the anode releases electrons towards the negative terminal and flows up to the cathode. One of the components of the lithium-ion battery is the cathode (6).

The process of converting chemical to electrical energy is called an electrochemical process (7). This electrochemical process that occurs at the battery electrodes is called the charge-discharge process. During the discharge process, Lithium (Li^+) ions are transferred, depicted by a small red circle, from the cathode to the anode and back during the charging process. Pure LiFePO_4 has Fe^{2+} ions in its valence state. The release of Li^+ ions causes defects so that LiFePO_4 tends to have Fe^{3+} ions. In addition, the change from Fe^{2+} to Fe^{3+} can be caused by the oxidation of the Fe atom. Li^+ ions are released from the anode and fill the cathode during the discharge process. Meanwhile, Li^+ ions move from the cathode to the anode in the charging process. The charge/discharge mechanism can be explained by the electrochemical reactions that occur during charging are shown in Equation 1, while during discharge they are shown in Equation 2.



LiFePO_4 has great potential as cathode material for lithium-ion batteries because of its low toxicity, high charging-discharging capacity of 170 mAh.g^{-1} , excellent safety profile, and favorable economic advantages. Meanwhile, lithium-ion batteries that are composed of pure LiFePO_4 cathode material have several disadvantages, including short charge-discharge cycles, short battery life, and long charging processes but fast discharging processes that make battery performance less than optimal. However, the lack of performance of the battery cathode is due to the low conductivity and the low ion-diffusion rate, thus inhibiting its future development. In addition, some previous studies have shown that pure LiFePO_4 cathode materials also have lower capacitance compared to LFP cathodes that are treated with atomic doping and carbon coating (8).

To overcome these weaknesses, surface modification by coatings is often utilized. This aims to avoid unwanted interactions between electrodes and electrolytes. This method can improve the thermal and structural stability as well as the chemical and mechanical properties of cathode materials (9). The three-dimensional carbon coating on LiFePO_4 enhances its high capacity, superior electrical conductivity, and minimal volumetric expansion, facilitating more efficient electron transport pathways (10). Besides coatings, doping can be applied to modified lithium oxides. Doping is the addition of a few heteroatoms that are incorporated into the host crystal structure without the appearance of additional phases. Since the structure of lithiated oxides and their electrochemical properties can vary greatly, this approach is often used to control the behavior of active materials (9).

The need for battery technology is a major requirement nowadays. The use of electronic divisions is increasing among the public, so research on battery cathode materials needs to be continuously developed. The development of this research is shown by innovations in material synthesis techniques, including coating techniques and doping techniques. This article will further discuss research that develops new techniques for improving the performance of battery cathodes, especially in lithium-ion batteries. Herein, the purpose of this review is to show material development methods with atomic doping and carbon coating techniques towards improving battery cathode performance, such as the enhancement of discharge capacitance, especially in lithium-ion batteries. This study also summarizes atoms for doping technique and their effect on olivine crystal

structure. Furthermore, it also discusses materials that can be used as coatings.

II. CRYSTAL ARRANGEMENT OF LiFePO₄

LiFePO₄ exhibits the structure of FeO₆ octahedra and PO₄ tetrahedra. These tetrahedra share oxygen atoms with adjacent PO₄ tetrahedra and FeO₆ octahedra. Lithium ions are positioned between the FeO₆ octahedra and PO₄ tetrahedra. The oxygen atoms in LiFePO₄ adopt a configuration where each is coordinated by one Fe and one P atom. In some lithium-based oxide cathode materials, structural degradation can occur due to the migration of metal ions from octahedral to tetrahedral sites (10). LiFePO₄ exhibits a characteristic olivine-type crystalline structure with a lattice arrangement categorized under the P lattice type. The space group's name is Pnma. Lattice parameters of LiFePO₄ are a, b, c = 10.3297, 6.0115, 4.7017 Å and $\alpha = \beta = \gamma = 90^\circ$ (11). The structure of LiFePO₄ is shown in Figure 1 illustrated using Vesta software.

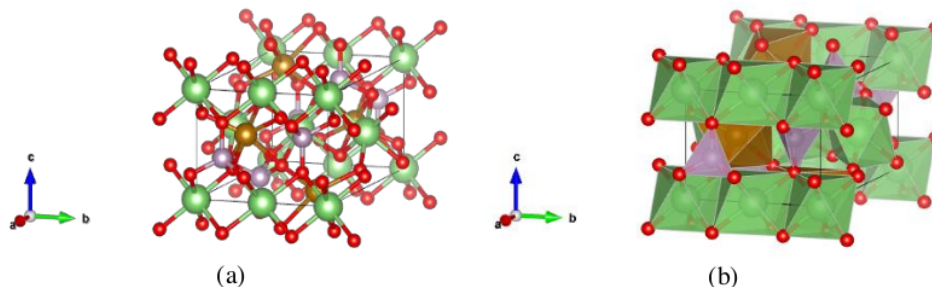


Figure 1. The olivine structure of LiFePO₄ with different views (a) ball and stick view showing red for oxygen atom, green for lithium atom, brown for ferrous atom, and purple for phosphate atom; (b) polyhedral view showing the FeO₆ octahedra (green), PO₄ tetrahedra (purple), and one-dimensional tunnels in which the lithium ions reside.

Olivine-structure of LiFePO₄ is considered a promising cathode material for lithium-ion batteries (12, 13). Olivine structure is a hexagonally close-packed oxygen array, in which the octahedra share both edges and faces. LiFePO₄ initially includes one Li⁺ ion per formula unit that can be extracted and transferred to the anode in the first charge process, compensating for the oxidation of iron (Fe²⁺ to Fe³⁺) (13). The transfer of lithium ions occurring at the interface between the electrode and electrolyte, alongside the lithium translocation within the active materials and porous electrode space, constitutes a pivotal phenomenon during the charging-discharging cycles of batteries. The efficiency of these processes significantly influences the overall battery performance, as highlighted by Qianru Shi (14). The limited electrical and ionic conductivity exhibited by LiFePO₄ contributes to its diminished rate capacity and utilization. Addressing these limitations has emerged as a critical focus of research, as emphasized by Satyavani (2).

III. SYNTHESIS METHOD OF LiFePO₄

There are several methods in the synthesis of LiFePO₄-based cathode materials such as solvothermal, hydrothermal, sol-gel, solid state, citrate process, and dissolution method. LiFePO₄ was synthesized using solvothermal in several studies (10, 15). The solvothermal method used a solvent for the synthesized process under elevated temperature (100-1000°C) and pressure (1-10.0 atm) (16). Solid state method is also used for LiFePO₄ synthesized material (17, 18, 19, 20). The solid-state method is the most common method for preparing powders and is generally used for the mass production of unique and advanced structures. This method is simple and easy to industrialize (2). The hydrothermal method was also used in several studies to synthesize LiFePO₄ materials (3, 21). The hydrothermal process involves a heterogeneous chemical reaction occurring within an aqueous medium subjected to elevated pressure and temperature conditions. This method facilitates the dissolution and subsequent recrystallization of substances that exhibit limited solubility under standard environmental circumstances (Shaikh et al., 2020). On the other hand, the

sol-gel technique represents an effective approach for attaining targeted particle dimensions with precise stoichiometry, while requiring a reduced calcination temperature and yielding high product quantities. In the specific case of LiFePO_4 , carbon coating was applied to integrate the organic additive during an intermediate grinding phase after initial decomposition at 500°C . This improved the rate-ability of the sol-gel material (11). Other synthesized methods for LiFePO_4 material are the citric acid process Method (22) and the dissolution method (23).

The development of LiFePO_4 material for lithium-ion battery electrodes makes researchers innovate to improve this performance. There are several kinds of techniques used to make LiFePO_4 material that are increasingly useful. This article presents two techniques that have been widely used in several studies, coating and atomic doping method in LiFePO_4 -based material.

IV. COATING METHOD OF LiFePO_4

The application of coating techniques has emerged as a pivotal strategy in enhancing the efficiency of materials. Coating, as a method of coverage applied to object surfaces, serves to enhance various surface properties of the substrate, encompassing aspects such as visual aesthetics, adhesion, corrosion resistance, and wear resistance, among others (24). Various coating methods cater to diverse application needs, all unified by the overarching objective of safeguarding components or structures from potential mechanical or chemical harm (25).

The advantages of carbon coating were highlighted, focusing on its application to newly developed photocatalyst particles and electrode materials for lithium-ion rechargeable batteries. Carbon materials have found widespread application owing to their favorable attributes, including elevated electrical and thermal conductivity, as well as robust thermal and chemical stability (26). A widely used technique to increase the conductivity of LiFePO_4 is carbon coating electrons (14). The electrochemical efficiency of LiFePO_4 -coated carbon electrodes relies on the choice of carbon precursor, which encompasses organic, inorganic, polymer, and biomass sources. (27).

Elevated levels of carbon are anticipated to enhance the diffusion rate of Li^+ ions across carbon layers. The transfer of lithium ions at the electrode-electrolyte interface, alongside their movement within active materials and the porous electrode structure, constitutes a pivotal aspect of battery charge-discharge cycles. The kinetics of these processes significantly enhance the battery's overall performance. Consequently, battery electrodes must exhibit robust lithium ion and electron conductivity to facilitate the efficient transport of lithium ions and electrons. (14). The application of a carbon coating additionally diminishes the particle size of LiFePO_4 by impeding particle expansion throughout the sintering procedure (28). The procedure involves applying carbon coatings using different carbon precursors, followed by high-temperature thermal treatment. This approach is characterized by its simplicity, feasibility, and suitability for large-scale industrial applications. The coating process serves to decrease the volumetric energy density of battery materials and constrain the diffusion of lithium ions.

The process of carbon coating on LiFePO_4 material used as electrode material has been carried out by many researchers using various thermal treatments in the synthesis process. Therefore, this article presents a comparison of the use of carbon sources, carbon coating synthesis methods, and the best capacitance values obtained from several studies. The comparison of capacitance values of LiFePO_4 electrodes treated with carbon coating is shown in Table 1.

Table 1. Comparison of synthesis method and best capacitance from each carbon source.

| Carbon Sources | Synthesis Method | Best Capacitance (mAhg ⁻¹) | Ref. |
|----------------|---|--|------|
| Glucose | Pyrolysis, annealed at 700°C for 5 hours under a N_2 atmosphere. | 162 | (3) |

| | | | |
|---|---|--------|------|
| Three-dimensional carbon from <i>Cetyltrimethyl Ammonium Bromide</i> (CTAB) | Solvothermal, stirring for 8 h and annealed at 500°C or 800°C for 3 hours in N ₂ . | 159.8 | (10) |
| Polypropylene | Solvothermal and carbonization at 650°C for 3 hours in Argon atmosphere | 80.9 | (15) |
| Glucose | Solid state reaction, dry mixing, ball milling and calcined at 700°C for 8 hours under N ₂ atmosphere. | 160.1 | (17) |
| Glycine & MWCNT | Solid state reaction, sintered at 750°C for 6 hours in flowing Ar atmosphere, ball milling. | 130 | (18) |
| Tapioca and acetic acid (CH ₃ COOH) | Heated to 700°C for 20 minutes in a nitrogen atmosphere. | 35.58 | (19) |
| Glucose (C ₆ H ₁₂ O ₆) 11wt% | The carbonation process is conducted within a tube furnace at a temperature of 450°C for a duration of 2 hours under a Nitrogen atmosphere. | 78.745 | (20) |
| Carbon Nano Tube (CNT) | Hydrothermal Process, annealed in the tubular furnace at 700°C for 6 hours under Argon atmosphere | 106.84 | (29) |

Based on Table 1, it is obtained that the carbon coating synthesis method for LiFePO₄ material uses a carbonization temperature range between 450°C and 700°C. In addition, several studies use natural materials as basic carbon materials, namely Glucose (20) and Tapioca (19). Besides carbon coatings, there were some other innovations with non-carbon coating in LiFePO₄ cathode materials. During the process of carbon coating, the augmentation in carbon content is observed [5] diminish the tap density of LFP particles. Conversely, the metal coating is shown to maintain the electronic density of LFP particles while [5] circumventing any reduction in tap density. Moreover, metal coating facilitates the formation of electron channels within the external layer of the cathode material, thereby enhancing the speed of electron transport (21). Common materials for surface coating that do not contain carbon include [4] metals, metal oxides, solid electrolytes, and ion-conducting materials. Gallium can be utilized to enhance the electrochemical performance and electron conductivity of LiFePO₄ (LFP) without compromising its original olivine structure (30). Furthermore, Gallium coating demonstrated that by modification of LiFePO₄ cathode materials with a combined gallium and carbon coating, the cycling performance and charge-discharge capacity are significantly improved compared to pristine LFP@C (21).

V. ATOMIC DOPING METHOD OF LiFePO₄

Doping is the process of adding very trace amounts of particular foreign atoms, called

dopants, to the crystal lattice to change the electrical characteristics (31). In addition, atomic doping also aims to increase the cell volume in the crystal structure without changing the crystal phase. Increasing the cell volume in the crystal structure is expected to improve electrochemical performance, especially in battery cathode materials. Atomic dopants that are commonly used are atoms that have adjacent atomic radii, where the atomic dopant has a larger radius than the original atom. One of the studies that carried out the atomic doping technique is the use of Silicon (Si) atomic dopants against Phosphate (P) atoms in the LiFePO_4 structure so that the structure becomes $\text{LiFeSi}_x\text{P}_{1-x}\text{O}_4$ (19, 20).

To review the atomic doping process, it is necessary to characterize the material. One of the characterization methods that can be used to ensure the atomic doping process occurs is XRD (X-ray Diffraction). XRD is a material characterization technique that is widely used to identify the structure and phase of a material. Several studies have successfully identified the material structure, especially in LiFePO_4 materials that are given atomic doping techniques or carbon coating techniques (17, 33). This article presents several studies that have successfully identified atomic doping events through XRD for material structure and Discharge Capacity for electrochemical performance which is shown in Table 2.

Table 2. Comparison of various atomic doping in LiFePO_4 materials in volume crystal and discharge capacity performance.

| Sample | Dopant Atom | Doping Site | Crystal Volume (\AA^3) | Discharging Capacity (mAhg^{-1}) | Ref. |
|--|------------------|-------------|-----------------------------------|---|------|
| LiFePO_4/C | - | - | 285.06 | N/A | (11) |
| $\text{LiFe}_{0.99}\text{Ru}_{0.01}\text{PO}_4/\text{C}$ | Ru | Fe | 281.64 | 162.6 - 110.6 | |
| LiFePO_4 | - | - | 286.87 | 64.4 - 49.3 | (15) |
| $\text{Li}_{0.99}\text{Na}_{0.01}\text{FePO}_4$ | Na^+ | Li | 287.79 | 80.9 - 70.1 | |
| LiFePO_4/C | - | - | 290.61 | 147.6 | (17) |
| $\text{LiFe}_{0.95}\text{Ce}_{0.05}\text{PO}_4/\text{C}$ | Ce^{3+} | Fe | 290.88 | 160.1 - 136.7 | |
| LiFePO_4/C | - | - | N/A | 130 - 20 | (18) |
| Co-doped LiFePO_4/C | Co | N/A | N/A | 110 - 70 | |
| LiFePO_4/C | - | - | 291.04 | 23.22 | (19) |
| $\text{LiFeSi}_{0.15}\text{P}_{0.85}\text{O}_4/\text{C}$ | Si | P | 291.14 | 35.58 | |
| LiFePO_4/C | - | - | 289.35 | 51.715 | (20) |
| $\text{LiFeSi}_{0.03}\text{P}_{0.97}\text{O}_4/\text{C}$ | Si | P | 290.78 | 78.745 | |
| LiFePO_4 | - | - | N/A | N/A | (23) |
| $\text{LiFe}_{0.98}\text{Cu}_{0.02}\text{PO}_4$ | Cu | Fe | 281.11 | 13.73 | |
| $\text{LiFePO}_4@\text{C}$ | - | - | 291.18 | 140 | (33) |
| $\text{LiFe}_{0.97}\text{In}_{0.03}\text{PO}_4$ | In | Fe | 291.55 | 150 | |
| LiFePO_4 | - | - | 287.04 | 88 | (34) |
| $\text{LiZn}_{0.01}\text{P}_{0.99}\text{O}_4$ | Zn | P | 293.54 | 133 | |
| $\text{LiFePO}_4@\text{C}$ | - | - | 290.65 | 138.7 | |

| | | | | | |
|--|----|----|--------|-------|------|
| LiFe _{0.98} Mn _{0.02} PO ₄ @C | Mn | Fe | 290.86 | 150.7 | (35) |
|--|----|----|--------|-------|------|

51
The X-ray diffraction (XRD) analysis revealed a notable augmentation in the crystalline volume of LiFePO₄-based materials across all doped variants while retaining the olivine structure indexed in orthorhombic P n m b. The introduction of a minor quantity of Cesium dopant atom did not disrupt the lattice configuration of LiFePO₄; rather, 22 led to an expansion in crystal volume. This phenomenon was accompanied by an increase in the lattice 18 parameters of all crystal cells, attributed to the incorporation of Ce³⁺ ions instead of Fe²⁺, possibly due to the larger ionic radius of Ce³⁺ (r = 0.114 nm) compared to Fe²⁺ (r = 0.074 nm) occupying the Fe sites (17). Conversely, XRD analysis of Ruthenium-doped samp 39 exhibited a reduction in the volume of LiFePO₄-based material crystals, accompanied by a decrease in lattice parameters. This reduction in lattice parameter shortens the path of Li⁺ movement and reduces diffusion distances in Ru-doped LiFePO₄ (11). Moreover, changing copper atoms or doping into the Iron sites may enhance the kinetics of electrochemical processes due to the increased electrical conductivity imparted by Cop 3r within the LiFePO₄-based material (23). Another study on Na⁺ atomic doping indicates that the lattice 3 ructure of LiFePO₄ was unaffected by a small amount of Na ion doping. Since the Na⁺ radius of 0.97 Å is 33 ger than the Li⁺ radius (0.68 Å), Na-doped LiFePO₄ had a larger lattice size than pure LiFePO₄, which was beneficial for the Li⁺ intercalation/deintercalation process (15).

Based on the crystal volume data presented in Table 2, it is evident that most LiFePO₄ samples doped with Si exhibit an increase in crystal volume. This increase is attributed to the expansion of the crystal lattice parameters, which occurs as the doping concentration rises. The introduction of Si ions, which possess larger crystal dimensions compared to P ions, results in the observed lattice parameter enlargement (19). Consequently, the enhancement of lattice parameters, particularly the 'x' parameter, is primarily due to the larger atomic diameter of Si relative to P atoms. This observation confirms the successful incorporation of Si into the parent phase without altering the overall crystal structure (20). Doping Ruthenium (Ru) into iron (136 sites demonstrates advantageous effects in enhancing electron and Li⁺ transmission capabilities through the reduction of lattice 14 ameters and band gap, alongside the elevation of Fermi energy. Ru 4 doping significantly improves both the lithium diffusion coefficient and electrical conductivity, 5 adding to a marked enhancement in electrochemical performance. Notably, a minimal level of Ru doping does not alter the ordered olivine structure of LiFePO₄ (11).

VI. 17 ELECTROCHEMICAL PERFORMANCE

The electrochemical performanc 26 f graphene-based materials depends on the components used in their construction, particularly on their surface area, redox couple, electroconductivity, and long-term stability. The electrochemical process 7 at takes place on lithium-ion battery electrodes consists of charging and discharging processes. The charging-discharging proces 42 occur due to electrochemical reactions at the respective electrodes, which are accompanied by a reversible (de) intercalation of Li⁺ ions into the host electrode structures. This reversibility is important to allow the battery to recharge. These reactions must be reversible to allow a high cycle life 23 the battery (36). Discharging capacity is the amount of charge stored by the electrode and the maximum dependable operating capability of a charge storage resource to discharge energy. A comparison of discharging capacity values is shown in Table 2. Based on several studies using atomic doping, show 43 n increase in the overall discharging capacity value, indicating that atomic doping techniques can improve the electrochemical performance of LiFePO₄ materials.

Furthermore, to explore the impact of doping atoms in LiFePO₄-based materials, the Electrochemical Impedance Spectroscopy (EIS) reveals that Ru doping results in the value of Li⁺ diffusion coefficient is $1.11 \times 10^{-11} \text{ cm}^2\text{s}^{-1}$ and has a low charge transfer resistance (R_{CT}) of 58.40 Ω. These EIS data show that doping LiFePO₄ with Ru can increase Li⁺ ion transfer. Additionally, the application of a carbon coating synergically affects the performance of LiFePO₄ (11). EIS tests demonstrate that a three-dimensional carbon coating on LiFePO₄ enhances the lithium-ion diffusion

rate, leading to an increased specific capacity of LiFePO_4 (21, 37).

IV. CONCLUSION

LiFePO_4 , a widely developed lithium-ion battery cathode material, exhibits an olivine crystal structure and oxygen atoms shared between neighboring PO_4 tetrahedra and FeO_6 octahedra. Several synthesis methods, including solvothermal, hydrothermal, sol-gel, solid-state, citrate process, and dissolution methods, have been employed to produce LiFePO_4 -based cathode materials. Among these, the solvothermal method is frequently utilized. To enhance electrode performance, atomic doping, and coating techniques are commonly applied. Notably, three-dimensional carbon coating has been shown to improve lithium-ion diffusion rates, thereby enhancing the specific capacity of LiFePO_4 . Continuous innovation in the fabrication and modification of LiFePO_4 , particularly through various doping atoms and carbon sources, holds promise for significant improvements in electrode performance.

REFERENCE

1. Yoshino A. Development of the lithium-ion battery and recent technological trends. *Lithium-Ion Batteries*. 2014;1–20. doi:10.1016/b978-0-444-59513-3.00001-7
2. Satyavani TVSL, Srinivas Kumar A, Subba Rao PSV. Methods of synthesis and performance improvement of lithium iron phosphate for high rate Li-ion batteries: A Review. *Engineering Science and Technology, an International Journal*. 2016 Mar;19(1):178–88. doi:10.1016/j.jestech.2015.06.002
3. Wang J, Gu Y-J, Kong W-L, Liu H-Q, Chen Y-B, Liu W. Effect of carbon coating on the crystal orientation and electrochemical performance of nanocrystalline LiFePO_4 . *Solid State Ionics*. 2018 Dec;327:11–7. doi:10.1016/j.ssi.2018.10.015
4. Zhao J-W, Zhao S-X, Wu X, Cheng H-M, Nan C-W. The double role of silicon in improving the rate performance of LiFePO_4 cathode materials. *Journal of Alloys and Compounds*. 2017 Mar;699:849–55. doi:10.1016/j.jallcom.2016.12.430
5. Shalaby MS, Alziyadi MO, Gamal H, Hamdy S. Solid-state lithium-ion battery: The key components enhance the performance and efficiency of the anode, cathode, and solid electrolytes. *Journal of Alloys and Compounds*. 2023 Dec;969:172318. doi:10.1016/j.jallcom.2023.172318
6. Bondarde MP, Jain R, Sohn JS, Lokhande KD, Bhakare MA, Dhumal PS, et al. Carbon-based anode materials for lithium-ion batteries. *Lithium-Sulfur Batteries*. 2022;521–45. doi:10.1016/b978-0-323-91934-0.00004-1
7. Chaudhary N, Khanuja M. Electrochemistry—concepts and methodologies. *Electrochemical Sensors*. 2022;31–50. doi:10.1016/b978-0-12-823148-7.00002-7
8. Liu J, Wang S, He J, Liang K, Li J, Huang X, et al. Based on N, F, and p co-doping biomass carbon to construct 3D porous carbon coated LiFePO_4 for preparing lithium-ion batteries. *Journal of Industrial and Engineering Chemistry*. 2024 Mar; doi:10.1016/j.jiec.2024.03.023
9. Ahaliabadeh Z, Kong X, Fedorovskaya E, Kallio T. Extensive comparison of doping and coating strategies for NI-rich positive electrode materials. *Journal of Power Sources*. 2022 Aug;540:231633. doi:10.1016/j.jpowsour.2022.231633
10. Wang C, Yuan X, Tan H, Jian S, Ma Z, Zhao J, et al. Three-dimensional carbon-coated LiFePO_4 cathode with improved Li-ion battery performance. *Coatings*. 2021 Sept 18;11(9):1137. doi:10.3390/coatings11091137
11. Gao Y, Xiong K, Zhang H, Zhu B. Effect of RU doping on the properties of LiFePO_4 /c cathode materials for lithium-ion batteries. *ACS Omega*. 2021 May 25;6(22):14122–9. doi:10.1021/acsomega.1c00595
12. Chen X, Li Y, Wang J. Enhanced electrochemical performance of LiFePO_4 originating

- from the synergistic effect of zno and C co-modification. *Nanomaterials*. 2020 Dec 23;11(1):12. doi:10.3390/nano11010012
13. Jugović D, Uskoković D. A review of recent developments in the synthesis procedures of lithium iron phosphate powders. *Journal of Power Sources*. 2009 May;190(2):538–44. doi:10.1016/j.jpowsour.2009.01.074
 14. Shi Q, Xue L, Wei Z, Liu F, Du X, DesMarteau DD. Improvement in LiFePO₄–Li Battery performance via poly(perfluoroalkylsulfonyl)imide (PFSI) based Ionene Composite Binder. *Journal of Materials Chemistry A*. 2013;1(47):15016. doi:10.1039/c3ta13364h
 15. Liu Y, Qin W, Zhang D, Feng L, Wu L. Effect of na⁺ in situ doping on lifepo₄/C cathode material for lithium-ion batteries. *Progress in Natural Science: Materials International*. 2021 Feb;31(1):14–8. doi:10.1016/j.pnsc.2020.10.006
 16. Shaikh SF, Ubaidullah M, Mane RS, Al-Enizi AM. Types, synthesis methods and applications of ferrites. *Spinel Ferrite Nanostructures for Energy Storage Devices*. 2020;51–82. doi:10.1016/b978-0-12-819237-5.00004-3
 17. Zhao N, Li Y, Zhi X, Wang L, Zhao X, Wang Y, et al. Effect of Ce³⁺ doping on the properties of LiFePO₄ cathode material. *Journal of Rare Earths*. 2016 Feb;34(2):174–80. doi:10.1016/s1002-0721(16)60011-x
 18. Cech O, Thomas JE, Sedlarikova M, Fedorkova A, Vondrak J, Moreno MS, et al. Performance improvement on LiFePO₄/C composite cathode for lithium-ion batteries. *Solid State Sciences*. 2013 Jun;20:110–4. doi:10.1016/j.solidstatesciences.2013.03.017
 19. Prihandoko B, Zainuri M, Kirana N, Priyono S, Nuroniah I. Synthesis and characterization of active cathode material of LIFESIXP1-XO₄/C with variation of doping si ions. *Materials Today: Proceedings*. 2019;13:59–64. doi:10.1016/j.matpr.2019.03.187
 20. Zainuri M, Triwikantoro, Zahra PA. Active materials lifesixp1-xo₄/c as lithium ion battery cathode with doping variations si ions (0≤x≤0,06). *Key Engineering Materials*. 2020 Aug;860:75–80. doi:10.4028/www.scientific.net/kem.860.75
 21. Yi D, Cui X, Li N, Zhang L, Yang D. Enhancement of electrochemical performance of lifepo₄@c by GA coating. *ACS Omega*. 2020 Apr 21;5(17):9752–8. doi:10.1021/acsomega.9b04165
 22. Kim S, Kim U, Kim J, Cho W. Synthesis of porous lifepo₄ cathode material by citrate process for lithium ion battery. *Journal of the Ceramic Society of Japan*. 2016;124(2):145–9. doi:10.2109/jcersj2.15212
 23. Firdausi A, Latif C, Nihlatunnur, Prihandoko B, Zainuri M, Pratapa S. Electrical characteristics of natural ironstone-derived LiFe_{0.99}Cu_{0.01}PO₄ and life_{0.98}cu_{0.02}po₄ powders. *AIP Conference Proceedings*. 2020; doi:10.1063/5.0015421
 24. Pattankude B, Balwan A. Review on Coating Process. *International Research Journal of Engineering and Technology*. 2019 Mar 6;(3):7980-7984
 25. Fotovvati B, Namdari N, Dehghanghadikolaei A. On coating techniques for Surface Protection: A Review. *Journal of Manufacturing and Materials Processing*. 2019 Mar 25;3(1):28. doi:10.3390/jmmp3010028
 26. Inagaki M. Carbon coating for enhancing the functionalities of materials. *Carbon*. 2012 Aug;50(9):3247–66. doi:10.1016/j.carbon.2011.11.045
 27. Ramasubramanian B, Sundarajan S, Chellappan V, Reddy MV, Ramakrishna S, Zaghib K. Recent development in carbon-lifepo₄ cathodes for lithium-ion batteries: A mini review. *Batteries*. 2022 Sept 21;8(10):133. doi:10.3390/batteries8100133
 28. Zhang W-J. Structure and performance of Lifepo₄ Cathode Materials: A Review. *Journal of Power Sources*. 2011 Mar;196(6):2962–70. doi:10.1016/j.jpowsour.2010.11.113
 29. Honggowiranto W, Kartini E, Sudaryanto, Rofika RN, Hutamaningtyas E, Subhan A, et al. Improving performance of Lifepo₄ by addition of Carbon Nano Tube for lithium ion battery. *IOP Conference Series: Materials Science and Engineering*. 2019 Nov 1;553(1):012060. doi:10.1088/1757-899x/553/1/012060
 30. Zhao Q, Yu Y, Ouyang Q, Hu M, Wang C, Ge J, et al. Surface modification of Lifepo₄ by

- coatings for improving of lithium-ion battery properties. *International Journal of Electrochemical Science*. 2022 Nov;17(11):221142. doi:10.20964/2022.11.31
31. Ghosh A, Mohammed OF, Bakr OM. Atomic-level doping of metal clusters. *Accounts of Chemical Research*. 2018 Nov 19;51(12):3094–103. doi:10.1021/acs.accounts.8b00412
 32. Lee H, Yanilmaz M, Toprakci O, Fu K, Zhang X. A review of recent developments in membrane separators for rechargeable lithium-ion batteries. *Energy Environ Sci*. 2014;7(12):3857–86. doi:10.1039/c4ee01432d
 33. Lin W, Yang P, Zhou K, Wang L, Shen C. Indium doping: An effective route to optimize the electrochemical performance of Lifepo4 Cathode material. *Solid State Ionics*. 2023 Dec;403:116322. doi:10.1016/j.ssi.2023.116322
 34. Liu H, Cao Q, Fu LJ, Li C, Wu YP, Wu HQ. Doping effects of zinc on LiFePO4 cathode material for lithium ion batteries. *Electrochemistry Communications*. 2006 Oct;8(10):1553–7. doi:10.1016/j.elecom.2006.07.014
 35. Chen W, Song F, Yang Y, Chen Q. MN-doped LiFePO4@C as a high-performance cathode material for lithium-ion batteries. *Particuology*. 2024 Jul;90:418–28. doi:10.1016/j.partic.2024.01.012
 36. Kumar. Comparison on study of lithium ion and lead acid charging and discharging characteristics. *International Scientific Journal of Engineering and Management*. 2023 Mar 28;02(03). doi:10.55041/isjem00163
 37. Wang C, Yuan X, Tan H, Jian S, Ma Z, Zhao J, et al. Three-dimensional carbon-coated LiFePO4 cathode with improved Li-ion battery performance. *Coatings*. 2021 Sept 18;11(9):1137. doi:10.3390/coatings11091137

ORIGINALITY REPORT

19%
SIMILARITY INDEX

10%
INTERNET SOURCES

15%
PUBLICATIONS

4%
STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|--|-----|
| 1 | docplayer.info Internet Source | 1 % |
| 2 | Dragana Jugović, Dragan Uskoković. "A review of recent developments in the synthesis procedures of lithium iron phosphate powders", Journal of Power Sources, 2009 Publication | 1 % |
| 3 | Yan Liu, Wenchao Qin, Dengke Zhang, Liwei Feng, Lei Wu. "Effect of Na ⁺ in situ doping on LiFePO ₄ /C cathode material for lithium-ion batteries", Progress in Natural Science: Materials International, 2020 Publication | 1 % |
| 4 | Tianyu Zhao, Harshit Mahandra, Rajashekhar Marthi, Xiaobo Ji et al. "An overview on the life cycle of lithium iron phosphate: synthesis, modification, application, and recycling", Chemical Engineering Journal, 2024 Publication | 1 % |
| 5 | Dawei Yi, Xumei Cui, Nali Li, Liu Zhang, Dingyu Yang. " Enhancement of | 1 % |

Electrochemical Performance of LiFePO @C by Ga Coating ", ACS Omega, 2020

Publication

| | | |
|----|--|------|
| 6 | www.mdpi.com Internet Source | 1 % |
| 7 | Yuping Wu. "Lithium-Ion Batteries - Fundamentals and Applications", CRC Press, 2019 Publication | 1 % |
| 8 | zombiedoc.com Internet Source | 1 % |
| 9 | Can Wang, Xunlong Yuan, Huiyun Tan, Shuofeng Jian, Ziting Ma, Junjie Zhao, Xuewen Wang, Dapeng Chen, Yifan Dong. "Three- Dimensional Carbon-Coated LiFePO ₄ Cathode with Improved Li-Ion Battery Performance", Coatings, 2021 Publication | 1 % |
| 10 | Nanostructure Science and Technology, 2016. Publication | <1 % |
| 11 | acris.aalto.fi Internet Source | <1 % |
| 12 | www.researchgate.net Internet Source | <1 % |
| 13 | Y. Sundarayya, K.C. Kumara Swamy, C.S. Sunandana. "Oxalate based non-aqueous sol- | <1 % |

gel synthesis of phase pure sub-micron
LiFePO₄", Materials Research Bulletin, 2007

Publication

14

T.V.S.L. Satyavani, A. Srinivas Kumar, P.S.V. Subba Rao. "Methods of synthesis and performance improvement of lithium iron phosphate for high rate Li-ion batteries: A review", Engineering Science and Technology, an International Journal, 2016

Publication

<1 %

15

Submitted to University of Sheffield

Student Paper

<1 %

16

JinKiong Ling, Chelladurai Karuppiah, Syam G. Krishnan, M. V. Reddy et al. "Phosphate Polyanion Materials as High-Voltage Lithium-Ion Battery Cathode: A Review", Energy & Fuels, 2021

Publication

<1 %

17

Submitted to Amman Academy

Student Paper

<1 %

18

Hui Li, Ying Bai, Feng Wu, Qiao Ni, Chuan Wu. " Na-Rich Na V Ni (PO) /C for Sodium Ion Batteries: Controlling the Doping Site and Improving the Electrochemical Performances ", ACS Applied Materials & Interfaces, 2016

Publication

<1 %

19

Submitted to Staffordshire University

Student Paper

<1 %

20

Fei Guo, Xiaoqi Huang, Yudong Li, Shaohui Zhang, Xiong He, Jinghua Liu, Zhiqiang Yu, Feng Li, Baosheng Liu. "In Situ Low-Temperature Carbonization Capping of LiFePO₄ with Coke for Enhanced Lithium Battery Performance", Molecules, 2023

Publication

<1 %

21

Jiajun Wang, Xueliang Sun. " Olivine LiFePO₄ : the remaining challenges for future energy storage ", Energy & Environmental Science, 2015

Publication

<1 %

22

Nannan ZHAO, Yongsheng LI, Xiaoke ZHI, Li WANG, Xinxin ZHAO, Yamian WANG, Guangchuan LIANG. "Effect of Ce³⁺ doping on the properties of LiFePO₄ cathode material", Journal of Rare Earths, 2016

Publication

<1 %

23

Submitted to Technological Institute of the Philippines

Student Paper

<1 %

24

www.semanticscholar.org

Internet Source

<1 %

25

Jawahar Paulraj, Prasun Chakraborti, V. Anandakrishnan, S. Sathishkumar. "Tribo-

<1 %

Behaviors of Biomaterials and Their Applications - Fundamentals, Recent Advancements, and Future Trends", CRC Press, 2024

Publication

26

Karim Kakaei, Mehdi D. Esrafil, Ali Ehsani. "Graphene-Based Electrochemical Supercapacitors", Elsevier BV, 2019

Publication

<1 %

27

iris.unige.it

Internet Source

<1 %

28

nlist.inflibnet.ac.in

Internet Source

<1 %

29

repositorium.uminho.pt

Internet Source

<1 %

30

ses.library.usyd.edu.au

Internet Source

<1 %

31

Hossein Pourrahmani, Martin Gay, Adel Yavarinasab, Jan Van herle. "Optimization and dynamic responses of an integrated fuel cell and battery system for an 800kW ferry: A case study", Energy Reports, 2022

Publication

<1 %

32

Mochamad Zainuri, Triwikantoro, Pelangi Az Zahra. "Active Materials $\text{LiFeSi}_x\text{P}_{1-x}\text{O}_4/\text{C}$ as Lithium Ion Battery Cathode with Doping

<1 %

Variations Si Ions ($0 \leq x \leq 0,06$)", Key Engineering Materials, 2020

Publication

33

www.sciencegate.app

Internet Source

<1 %

34

www.wjgnet.com

Internet Source

<1 %

35

Aleksei V. Kubarkov, Alexander V. Babkin, Oleg A. Drozhzhin, Keith J. Stevenson, Evgeny V. Antipov, Vladimir G. Sergeyev.

"Engendering High Energy Density LiFePO₄ Electrodes with Morphological and Compositional Tuning", Nanomaterials, 2023

Publication

<1 %

36

Kamila Akhmetova, Fail Sultanov, Almagul Mentbayeva, Nurzhan Umirov, Zhumabay Bakenov, Batukhan Tatykayev. "Advances in multi-element doping of LiFePO₄ cathode material for capacity enhancement in Li-ion batteries", Journal of Power Sources, 2024

Publication

<1 %

37

Ma, Jun, Pu Hu, Guanglei Cui, and Liquan Chen. "Surface and Interface Issues in Spinel LiNi_{0.5}Mn_{1.5}O₄: Insights into a Potential Cathode Material for High Energy Density Lithium-Ion Batteries", Chemistry of Materials

Publication

<1 %

| | | |
|-------------|---|------|
| 38 | Qing Lin, Kaimin Su, Yajun Huang, Yun He, Jianbiao Zhang, Xingxing Yang, Huiren Xu. "Molecular Crystal Structure Simulations and Structure-Magnetic Properties of LiFePO ₄ Composite Particles Optimized by La", <i>Molecules</i> , 2024 | <1 % |
| Publication | | |

| | | |
|-------------|--|------|
| 39 | Shi-Peng Chen, Dan Lv, Jie Chen, Yu-Hang Zhang, Fa-Nian Shi. " Review on Defects and Modification Methods of LiFePO Cathode Material for Lithium-Ion Batteries ", <i>Energy & Fuels</i> , 2022 | <1 % |
| Publication | | |

| | | |
|-------------|---|------|
| 40 | Shruti Kaushik, Tushar Mehta, Prakash Chand, Swati Sharma, Gulshan Kumar. "Recent advancements in cathode materials for high-performance Li-ion batteries: Progress and prospects", <i>Journal of Energy Storage</i> , 2024 | <1 % |
| Publication | | |

| | | |
|-----------------|----------------------------------|------|
| 41 | encyclopedia.pub | <1 % |
| Internet Source | | |

| | | |
|-----------------|-------------------------------|------|
| 42 | etd.uwc.ac.za | <1 % |
| Internet Source | | |

| | | |
|-----------------|--------------------------------|------|
| 43 | hdl.handle.net | <1 % |
| Internet Source | | |

| | | |
|-----------------|---------------------------------------|------|
| 44 | jfu.fmipa.unand.ac.id | <1 % |
| Internet Source | | |

| | | |
|----|---|------|
| 45 | mdpi-res.com Internet Source | <1 % |
| 46 | pedro.unifei.edu.br Internet Source | <1 % |
| 47 | pubs.rsc.org Internet Source | <1 % |
| 48 | www.cell.com Internet Source | <1 % |
| 49 | Inagaki, M.. "Carbon coating for enhancing the functionalities of materials", Carbon, 201208 Publication | <1 % |
| 50 | Renato Gonçalves, Juliana Oliveira, Marco P. Silva, Pedro Costa et al. "Poly(styrene-butene/ethylene-styrene): A New Polymer Binder for High-Performance Printable Lithium-Ion Battery Electrodes", ACS Applied Energy Materials, 2018 Publication | <1 % |
| 51 | T.S. Srivatsan, Manoj Gupta. "High Entropy Alloys - Innovations, Advances, and Applications", CRC Press, 2020 Publication | <1 % |
| 52 | Tianshun Yao, Huan Zhang, Cai Qi, Jun Ma, Zihao Zhou, Quan Sun, Li Song, Yachao Jin, Mingdao Zhang. "Effective regeneration of | <1 % |

waste LiFePO4 cathode material by Cu doping modification", Applied Surface Science, 2024

Publication

Exclude quotes Off
Exclude bibliography On

Exclude matches Off